

VERY HEAVY WALL X-70 DSAW PIPE FOR TENSION LEG APPLICATION

Oskar Reepmeyer¹, Wolfgang Schuetz², Andreas Liessem¹, Fabian Grimpe³

¹EUROPIPE GmbH
Pilgerstraße 2, 45473 Muelheim, Germany

²Dillinger Huette
P.O. Box 1580, 66748 Dillingen, Germany

³Mannesmannroehren Muelheim GmbH
Wiesenstraße 36, 45473 Muelheim, Germany

Key Words: Tendon Pipes, HAZ toughness, ovality, straightness, heavy wall

Abstract

Assembled to strings Tendon Pipes connect the Tension Leg Platform (TLPs) and it's topsides with the sea floor. So far a water depth of 5,000 feet has been considered the limit for TLPs. New TLP concepts are passing this limit approaching 10,000 feet. The new larger oil and gas fields, specially in the Gulf of Mexico (GoM), are being expected in waters of 7,000 feet and more. Pipes in the 40 mm plus (1.6") wall range are requested for these water depths. These pipes have to fulfill extreme tight tolerance and toughness requirements. This article discusses the manufacturing of these pipes with the SAW UOE process. Experience and data out of order executions and trials are presented.

Introduction

Assembled to strings Tendon Pipes connect the Tension Leg Platform (TLP) and it's topsides with the sea floor (Figure 01). The platform is slightly submerged so that the natural buoyancy of the structure applies a tension on the vertical pipe strings. This principle provides the most stable system beside gravity based platforms with only little movements as reaction to the waves and current. So called dry well heads are possible. The maximum realized water depth for a TLP project has been so far 4,700 feet in the Gulf of Mexico. New TLP concepts are under investigation to pass 5,000 feet and going even beyond 7,500 feet. The new larger oil and gas fields in the GoM are in the 6,000 to 7,000 feet range. Reaching these water depths the Tendon Pipes carry not only the loads from the platform but in addition the collapse pressure of such water depths.

These new designs request pipes with a wall thickness of about 40 mm (1.57"). EUROPIPE proved with already delivered pipes with a wall of 38 mm in the X-70 grade and with a trial production of 40 mm wall thickness X-70 pipes that these pipes can be supplied. So far Tendon Pipes have been used in the OD range of 26" to 40", in lengths of 56-59 feet in order to reduce the number of girth welds, and in the wall thickness range of 25 to 38 mm, mostly X-70 material.

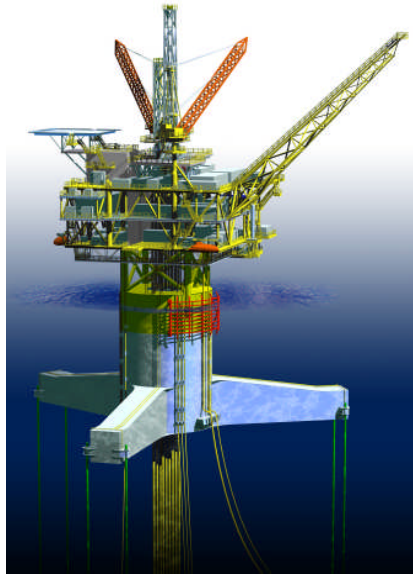


Figure 01: Principle of a TLP (the Atlantia Offshore Sea Star Design)

Fatigue is one of the main concerns for the tendon leg design. Due to the main load directions being perpendicularly to the girth weld the girth welds in the leg are considered to be more critical compared to the long seam which is only little exposed due to bending loads. Beside a high toughness of the material the fatigue resistance requires excellent geometry, specially at the pipe ends. Due to this the dimensional tolerances are very tight. Table 01 shows the common main dimensional requirements for these pipes. Additionally the weight is tolerated very tight in order to achieve neutral buoyancy of the legs.

	Tolerances
OD pipe ends	+/- 1.5 mm
Max. ovality pipe ends	5 mm (30% max)
Peaking	1.5 mm
Wall thickness	-1%/+3%
Straightness	14 mm for 18 m
Pipe weight	- 1%/+3%

Table: 01: Main Dimensional Requirements for Tendon Pipes.

Good toughness is requested for the base material (BM), weld material (WM) and the heat affected zone (HAZ) in order to provide a high defect tolerance level. The most economic production method for these pipes is the submerged arc welding process in two passes with the plates being

thermomechanically rolled. The manufacturing of DSAW pipes consist generally out of four principle production steps.




Figure. 02: Steps during DSAW manufacturing most important for tendon pipe manufacturing

Steps 1 to 3 of this manufacturing method are the most challenging to provide pipes with the required properties for this application (Figure. 02). High performance welding processes, DSAW for the not so critical long seam and multi layer SAW for the girth welds are characterized by a higher heat input with cooling conditions with impact on the toughness properties in the zone adjacent to the weld. The microstructure and herewith the toughness of this heat affected zone (HAZ) is mainly influenced by the cooling time $t_{8/5}$ from 800°C to 500°C, the maximum reheating temperature and the chemical composition of the base material. The HAZ is characterised by a wide range of different microstructures, depending on the distance from the fusion line and the cooling conditions. Generally the lowest toughness values are expected in the grain-coarsened heat affected zone (CGHAZ), as the toughness decreases with increased heat input and an increase in grain size. With increasing cooling time the microstructure in the HAZ is transformed from martensite to upper bainite as shown in Figure 03. This transformation to upper bainite is shifted to longer cooling times by significant additions of nickel which leads to lower FATT even at higher carbon equivalent.

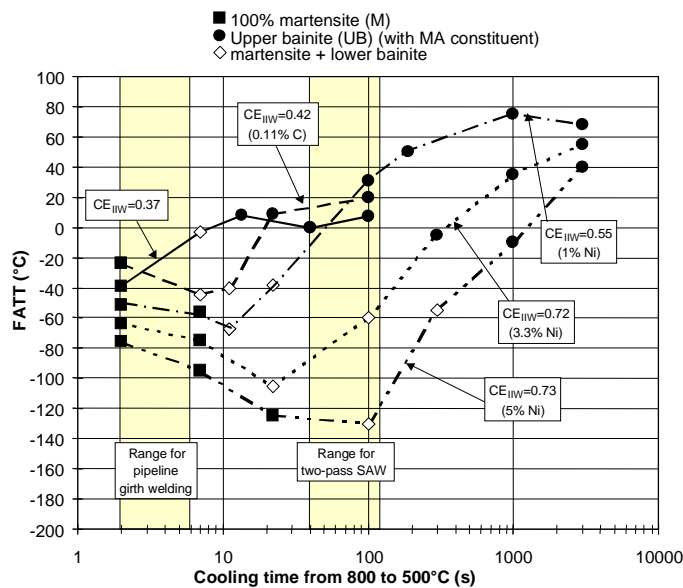


Figure 03: Correlation between FATT and the cooling time $t_{8/5}$ for different steel compositions and microstructures occurring in the CGHAZ (acc. [2,3])

The upper bainite is coarse grained and exhibits fractions of M-A constituents. Both microstructure features typically reveal low toughness properties. As the cooling conditions in two pass SAW welding remain virtually constant irrespective of wall thickness the grain growth and the formation

of M-A constituents has to be limited by appropriate chemical composition. The main measures currently known to improve HAZ toughness by optimised chemical composition are summarised in Table . Reduction of carbon plays the predominant role in avoiding the formation of M-A constituents. Furthermore the controlled use of limited additions of microalloying elements, e.g. Nb, is reported to inhibit the grain coarsening by formation of finely dispersed nitrides and/or oxides. These favourable effects have been confirmed by weld cycle simulation tests for a variety of steel compositions.

Measure	with positive influence on		Remarks
	FATT	upper shelf energy	
Reduction of C	●	●	Decreases hardenability & limits formation of M-A constituents
Limitation of Nb, V	●		Decreases hardenability & limits formation of M-A constituents
Controlled use of Ti	●	●	Restricts austenite grain coarsening
Addition of Ni	●		Retards the formation of upper bainite to longer cooling times
Low S, P, O		●	Reduces precipitations and segregations

Table 02: Improvement of HAZ toughness by adapted steel composition

The review of the published results shows that there is a fair level of understanding and that this knowledge is continually exploited in the steel chemistry and processing routes for line pipes, by which the overall HAZ toughness has been considerably improved and the statistical probability of having low toughness values in the HAZ has been reduced. Nevertheless values below the minimum requirement are still found due to the presence of LBZ's when the notch is favourably positioned in the CGHAZ. LBZ's are discrete microstructural regions of low toughness within the CGHAZ, but surrounded by microstructures with higher toughness. As the toughness of the CGHAZ depends mainly on the chemical conditions and the welding procedure (heat input, cooling time), which are technically constant due to strict control within narrow ranges for a specific line pipe production, it becomes obvious that LBZ are existing statistically distributed in each pipe of production. The number of LBZ's can be influenced and with this the probability to be discovered. The impact on the pipe integrity has been assessed (5,6). The result is that in a high quality steel with a low number of LBZ's the integrity of the pipes is not jeopardized.

Plate Production

The plates for EUROPIPE's pipe production are slab casted and rolled in the steel plants of EUROPIPE's mother companies. Used for the tendon pipe production and the 40 mm wall thickness trials were the "Dillinger Route" with slabs and plates produced in Dillinger and the "Mannesmann Route" with slabs from Huette Krupp Mannesmann (HKM) and the plate rolling performed at Mannesmannroehren Muelheim (MRM).

In consideration of the before discussed topics the analysis and rolling practice in the plate mill were adjusted accordingly. The common requirements for the mechanical properties of an API 5 L, X-70 tendon pipe are listed in Table 03. Specially the high level of toughness for the weld metal and the HAZ are remarkable.

Property	Requirements
YS, long. & transv.	70 – 85 ksi
TS, long. & transv.	82 – 97 ksi
CVN BM, -10°C	60/75 ft-lb
CVN WM, HAZ,-10°C	40/60 ft-lb
Shear area BM	85%
CTOD girth weld, 0°C	0,25/0.35 mm

Table 03: Common mechanical Requirements for Tendon Pipes (*Microalloying, Houston*)

Chemistry: Low carbon content and limited microalloying elements were chosen in order to improve weldability and to reduce the number of LBZs in the later HAZ as much as possible.

C	Mn	P	S	Ni	Nb+V+Ti	CE	PCM
0.05	1.6	0.010	0.001	0.4	<= 0.5	0.35	0.02

Table 04: Chemistry (average in %)

The average values of the elements used for wall thickness of 30 mm and heavier are listed in table 04. The somewhat negative impact of the microalloying elements on the HAZ toughness is very much overcompensated by the advantage of a low carbon content. According to table 02 the content of V and Nb should be limited. This has to be compensated by adding Ni in order to achieve X-70 properties.

Cleanness: The cleanliness of the steel, i.e. inclusion content and shape, reduced center line segregations and an excellent internal homogeneity is mandatory for the pipe ends. There negative impact on the fatigue exposed girth welds shall be minimized. Figure 05 describes the different steps applied. Reduction of carbon and phosphorus contents in the BOF converter with bottom stirring, de-sulphurization by degassing in a vacuum tank, expulsion of nitrogen and hydrogen. The result of this

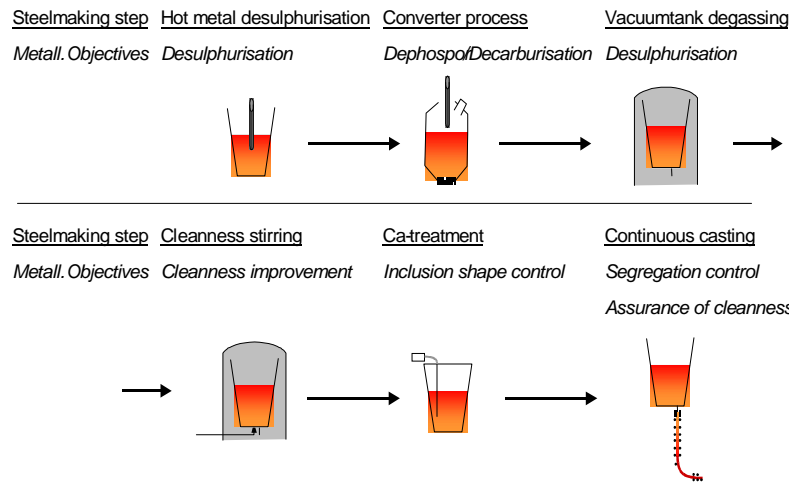


Figure 05: Steel making process, toughness optimized

treatment is a sulfur content of max. 0.001% in the finished cast. Additionally the molten steel is stirred with a ration optimized inert gas. This reduces the oxygen content to 0.002% max. A CaSi cored wire is used to shape control the melt.

Casting: The molten steek is continuously strand cast into slabs in a sealed off system including shrouding of the pouring stream. Soft reduction is applied to minimize centerline segregation. Bulging of the slabs between the rolls is prevented by an intensive cooling that results in low slab surface temperatures. This practice stiffens the shell of the strand.

Rolling: The Thermo-Mechanical-Control Process (TMCP) is employed to produce the plates. In this TMCP process the most important strengthening mechanisms and micro-structural features are employed as grain refinement by rolling in the non recrystallisation regime austenite, accelerated cooling (ACC), precipitation hardening (e.g. by NbCN) and dislocation hardening (e.g. due to finishing of rolling in two-phase $\alpha + \gamma$ - region).

Pipe Production

The pipes are manufactured in EUROPIPE's 18m line in Muelheim with the UOE process. To achieve the tight geometrical tolerances the forming process was optimized by FEA analysis. The simulation of the different forming steps, as shown in Figure 06 for the O-ing, results in a well adjusted forming chain and optimized tooling. Very important is the latest forming step, the cold expansion which is performed after the welding. This production step finalizes the geometry control and provides a stress homogenation function due to the plastic deformations implied.

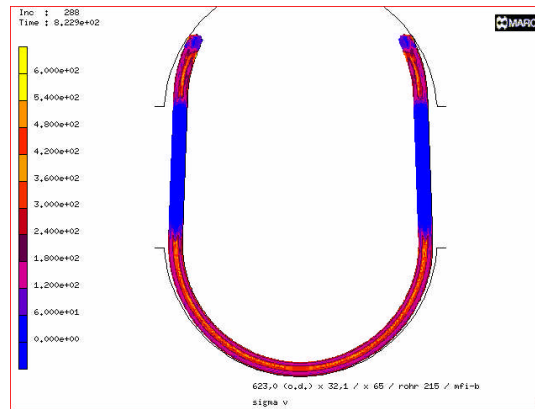


Figure 06: FEA Simulation of the O-ing Process

The welding process consists of a continuous GMAW tack welding followed by the main welding process. This is a two-pass welding operation beginning with a four wires inside welding and succeeded by a five wires outside welding. Inside and outside welding are submerged under flux. For a high toughness level of the WM a slightly basic flux is used. A balanced oxygen content in the WM is the result so that a fine grained acicular ferritic microstructure develops and the amount of oxide inclusions is minimized which supports high WM toughness levels. The chemical composition should avoid the formation of the lower toughness eutectoid ferrite. The WM composition should be as lean as possible. For this application a MoTiB based chemistry was selected for the wire providing the X-70 strength and the toughness required. The overmatching criteria for the long seam is fulfilled. The double seam arc welding process is based on a relative high heat input of about 9 kJ/mm and a short cooling time $t_{8/5}$ which results in the formation of some LBZ's as discussed before.

Production Results

Mechanical Properties

Figure 07 shows the strength distributions for executed orders with a wall thickness of 38 mm. Please notice the narrow window of 80/100 MPa achieved for both the longitudinal and transverse tensile tests. Longitudinal properties are requested due to the load situation of Tendon Pipes. The trial of with X-70 pipes with 40mm wall thickness produced a yield strength $Rt_{0,5}$ of 524 to 609 MPa and a tensile strength Rm between 655 and 689 MPa. This strength level was too high and can easily be adjusted in a later production. A leaner chemistry with a lower stress level will improve the toughness and the economics of the production.

In Figure 08 it can be seen that the charpy toughness values for the base material, the weld material and the fusion line are on a level with sufficient margin to the specified limits. The analysis concept discussed before leads to an excellent toughness. During 2004 new power sources were installed in our welding lines. Due to this a higher welding speed is possible resulting in a lower heat input which is favorable for the HAZ toughness. For the 40 mm wall thickness trial production the same analysis design provided also toughness values much better than the specified minimum as can be

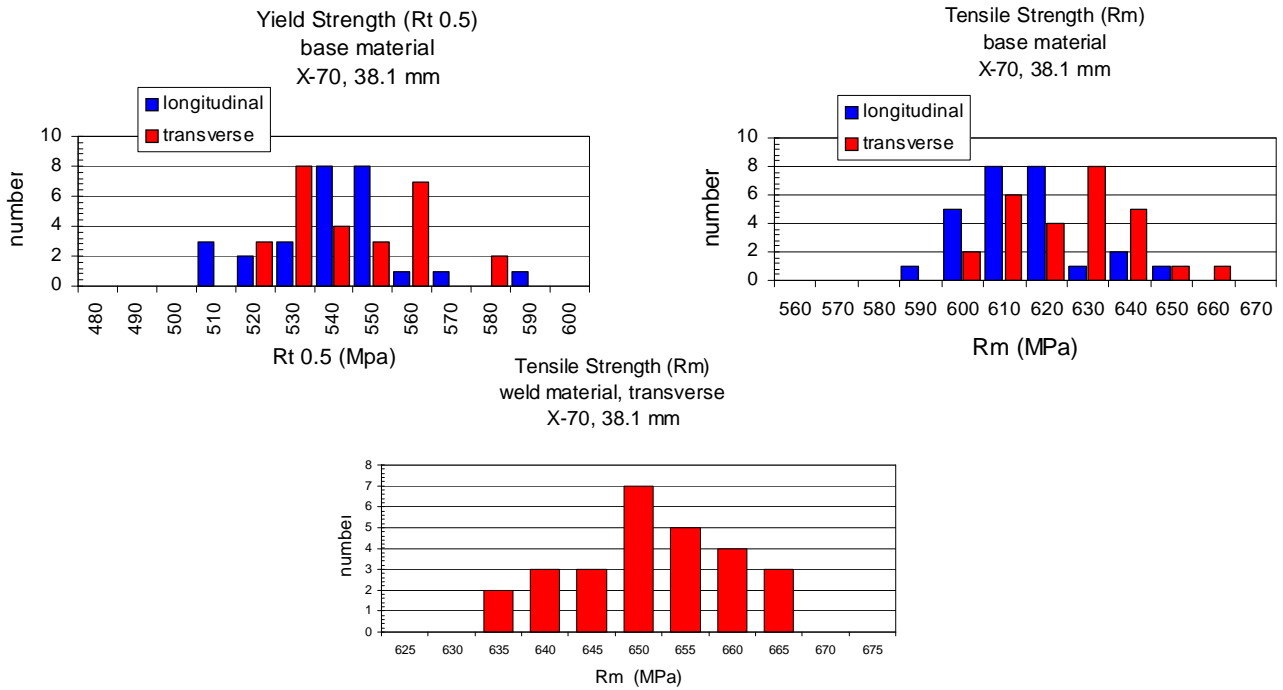


Figure 07: Strength distributions from orders with 38 mm wall thickness in X-70

seen in Figure 09. Due to these excellent results the qualification for walls heavier than the 38 mm was achieved.

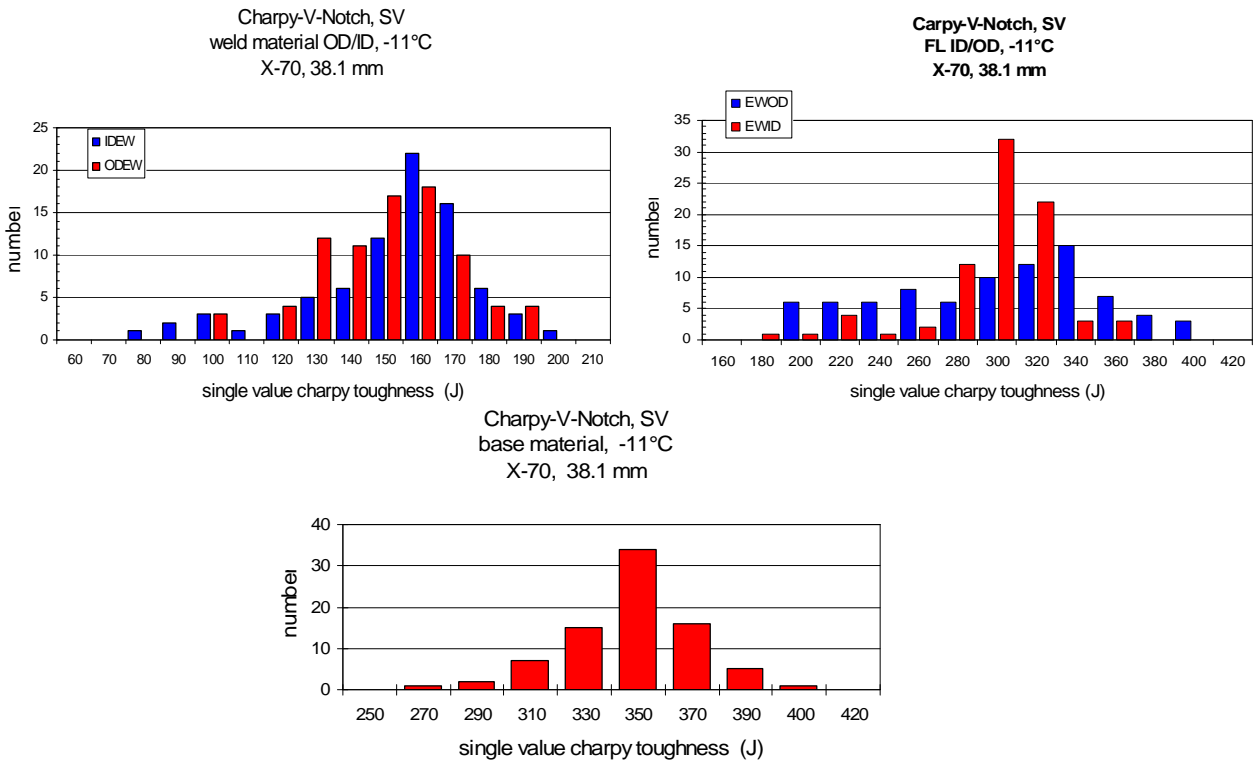


Figure 08: Charpy toughness Values (single values) for WM, HAZ (FL) and BM

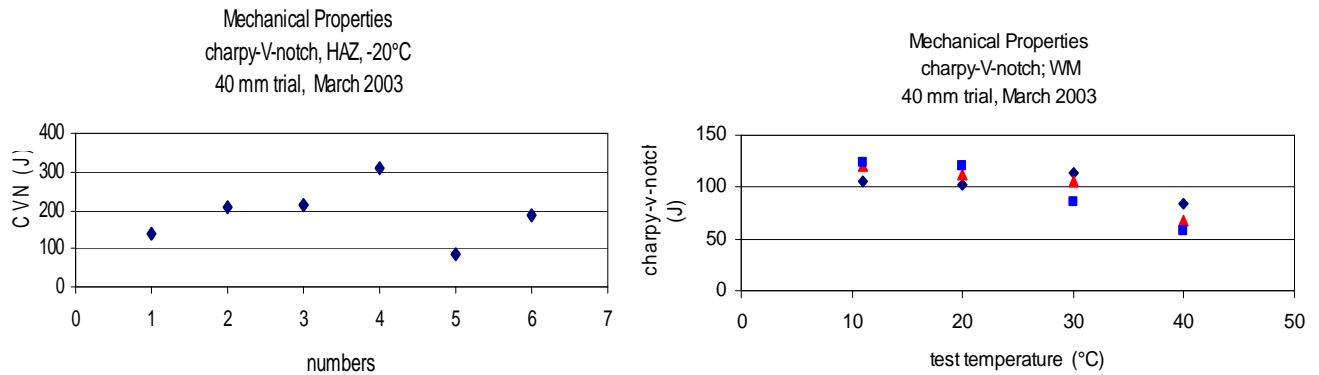


Figure 09: Charpy toughness Values (single values) for WM, HAZ (FL) for 40 mm wall

As mentioned already the girth weld is very much exposed to the main stresses in the tendon sections. The common fracture mechanical assessment of the girth weld is based on CTOD values.

The required values are very much driven by API RP 2Z. With today's knowledge these values are very conservative, specially with the NDT methods being applied today. Nevertheless, good past experience with this code, criticality of the weld and the regulatory status manifests this requirement.

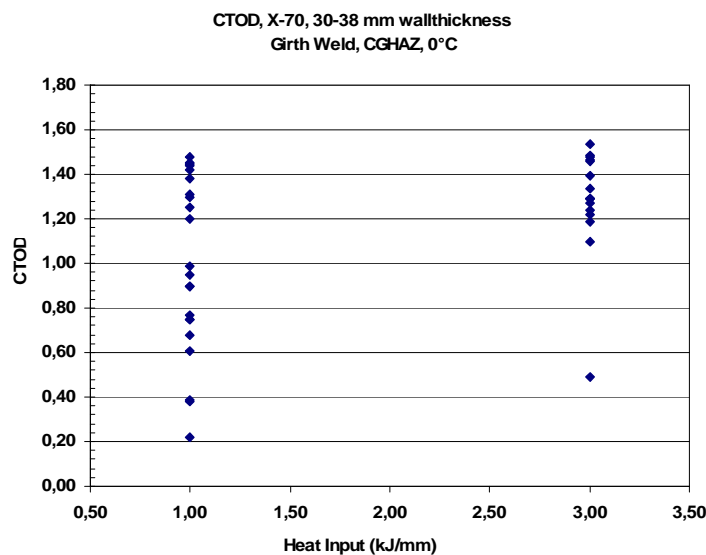


Figure 10: CTOD values (single values) of the girth weld

Figure 10 shows CTOD values achieved again over several orders with wall thickness between 30 and 38 mm. The girth welds were produced as requested with low heat input (1.0 kJ/mm) and high

heat input (3 kJ/mm). It can clearly be seen that the low heat input produces trend wise lower CTOD values in the coarse grain heat affected zones (CGHAZ) of the welds. Today fabrication yards are using mostly automated girth welding equipments with a heat input of 1.5 to 2.0 kJ/mm. The CTOD testing of welds produced with 0.8 -1.0 kJ/mm provides an already conservative value. The higher heat input is mostly used to cover repair welding procedures. For the 40 mm trials we received CTOD values of 0.26, 0.61 and 0.77 mm for the heat input of 1.0 kJ/mm and 1.10, 1.21 and 1.54 mm for 3.0 kJ/mm heat input. These results are again in compliance with the before mentioned values from executed orders for walls up to 38 mm.

Geometrical Properties

Also the geometry achieved for the 38 mm production and the 40 mm trial exceeded the limits specified by the TLP designers. To receive an outside diameter as close to nominal as possible is important because of the neutral buoyancy being desired for the tendon section in order to compensate the deviation with costly measures as buoyancy elements, etc. Figure 11 represents produced outside diameter and it's deviation from nominal. The narrow scatter band assures a matching of the pipe ends during girth welding with a very small high-low from pipe face to pipe face. These high-low steps are desired to be as small as possible to minimize the impact on the life time of the girth weld.

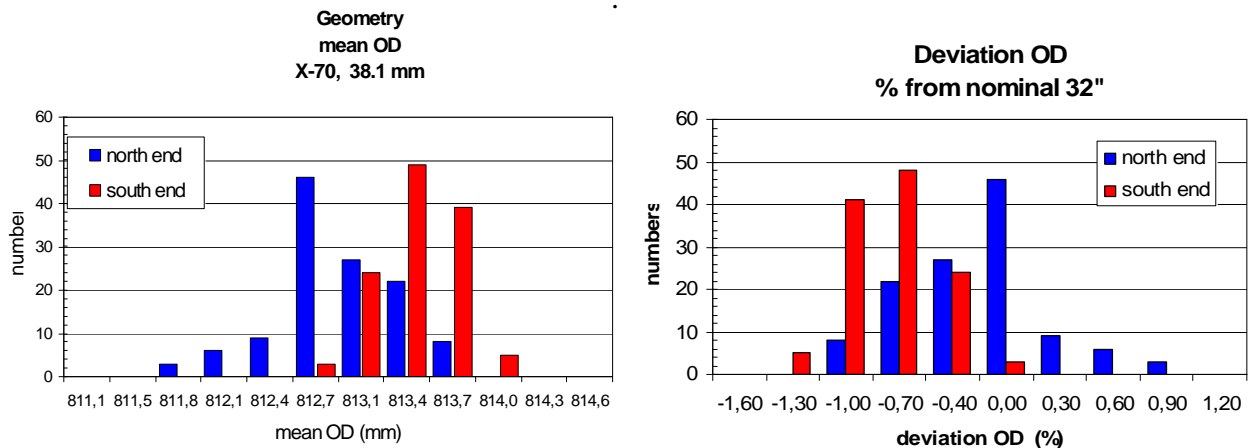


Figure 11: Deviation of the inside diameter in mm and in % of nominal ID for 38.1 mm wall

Beside the constant OD the second factor for this criteria is a very small out of roundness (OOR) of the pipe ends combined with a consistent appearance of the location of the long and short axis of the OOR from pipe to pipe in order to adjust the pipe ends accordingly before welding. Figure 12 exhibits OOR values. An excellent roundness is being provided and only a very small amount of pipes show OOR values larger than 3 mm. Additionally to the low absolute value also the shape of the pipe ends is very consistent. Figure 13 is characteristic for the appearance of the pipe ends.

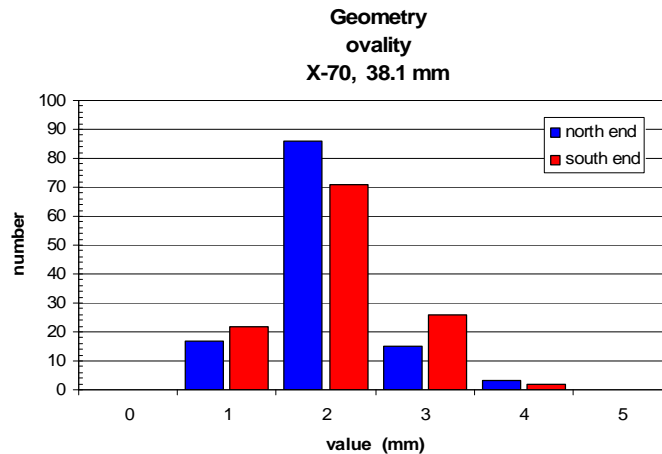


Figure 12: Out of roundness (OOR) values measured at orders with 38 mm wall

Please consider the very high magnification of the picture in Figure 13. This shape assures not only the desired little high-low's after alignment and before welding but also reduces the costly selection and positioning of the pipes during the welding preparation in the fabrication yard.

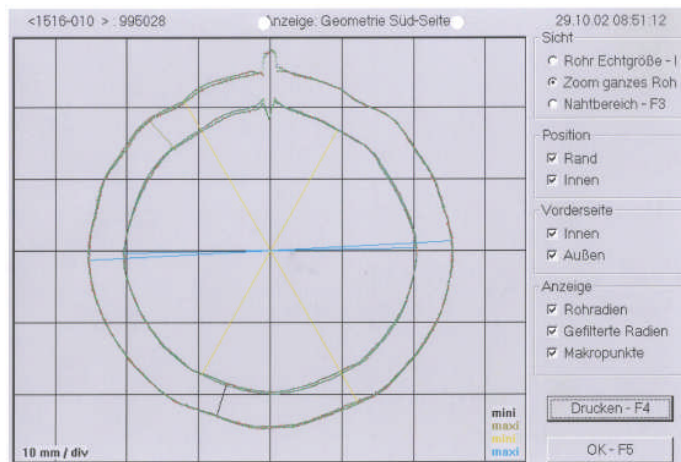


Figure 13: Characteristic shape of a pipe end

Buoyancy relevant is not only the outside diameter but also the wall thickness and with this the kg/m weight of the pipes. The distribution of the deviation from the nominal specific weight in [%] is shown in figure 14. It can be seen that the nominal metric weight combining all dimensional parameters is very close to the specified metric weight which should be somewhat in the plus tolerance and not in the minus tolerance. As discussed before this prevents costly measures to compensate weight differences for neutral buoyancy.

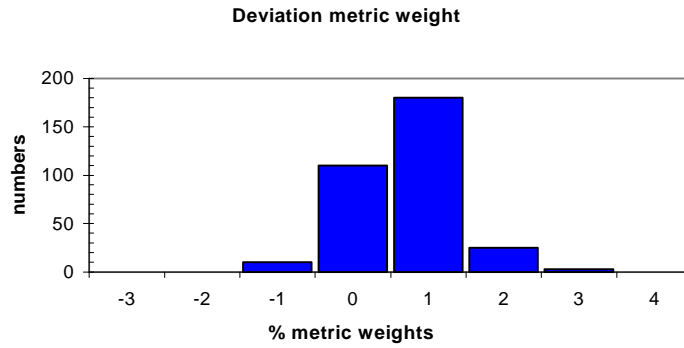


Figure 14: Distribution of the deviation from the nominal metric weight

The straightness of the pipes is the latest important parameter. The deviation of the straightness can result in a deflection of the axial stresses in the girth weld with a significant impact on the life time.

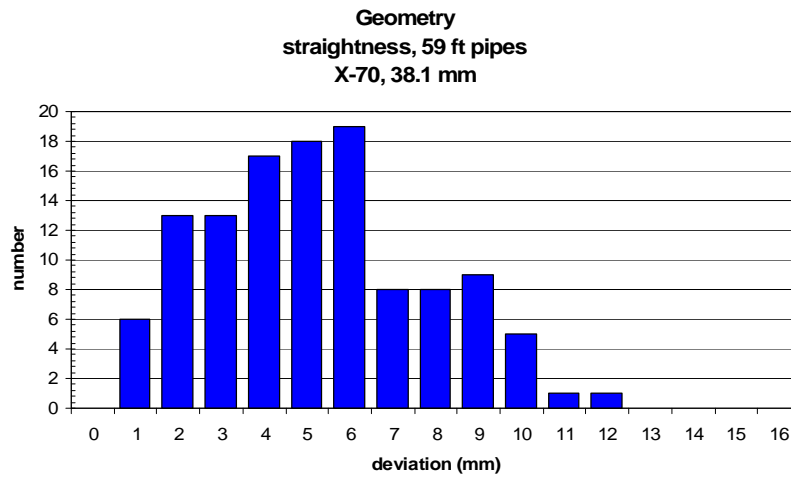


Figure 15: Distribution of the deflection from the straightness at over several orders

Figure 15 shows the distribution of the deviation from straightness for the 38.1 mm wall thickness orders. The very tight limits resulted in some cases into a rework in order to deliver the 15 mm maximum deviation for a 60 feet long pipe.

Conclusions

The extreme load scenario for tendon sections requires a pipe as close as possible to the ideal circle and straightness. A weight per meter as close as possible to the nominal weight results in cost savings for a neutral buoyancy situation. High toughness levels provide an excellent defect tolerance of the system under fatigue loads. The combination of the DSAW and UOE manufacturing process is the most cost efficient method to produce these pipes with a length up to 60 feet and a wall thickness up to 1.6". A fine tuned chemistry with a micro alloying concept including Nb is basis for the high toughness levels for these heavy wall plates and pipes. The supply of pipes with a wall thickness up to 1.60" in the grade X 70 in 60 ft length coming from the cost effective UOE DSAW manufacturing process is possible.

References

- 1 Graef, Michael, Niederhoff, Kurt
Properties of HAZ in two-pass submerged-arc welded large-diameter pipe
EUROPIPE publication, 2001
- 2 Graef, M. and K. Niederhoff
Toughness behavior of the heat affected zone (HAZ) in double submerged-arc welded large-diameter pipe; Pipeline Technology Conference, 15-18 October 1990, Oostende, Belgium
- 3 Andreas Liessem and Marion Erdelen-Peppler
A critical view on the significance of HAZ toughness testing
International Pipeline Conference, Calgary 2004
- 4 API RP 2Z, 1987, Recommended Practice for Production for Steel Plates for Offshore Structures, API, Washington, DC
- 5 Bai, Y., G. Knauf, G. Hillenbrand
Materials and Design of High Strength Pipelines
ISOPE-2000-YB-001
- 6 Fu, B., Guttormsen, S., Vu, D. Q., Chauhan, V., Nokleebye, A.
Significance of Low Toughness in the Seam Weld HAZ of a 42-inch Diameter Grade X-70 DSAW Line Pipe – Experimental Studies. Paper, 13th Biennial, 2002, Berlin